



EVALUATION OF SSNTD STACKS EXPOSED ON THE ISS

Joe K. Pálfalvi¹, Yu. Akatov², J. Szabó¹, L. Sajó-
Bohus³, and I. Eördögh⁴


¹Atomic Energy Research Institute, POB-49, H-1525
Budapest, Hungary

² Institute for Biomedical Problems, Moscow 123007, Russia

³ University Simon Bolivar, 89000 Caracas, Venezuela

⁴ Res. Inst. for Technical Physics and Material Sci. POB-49,
H-1525 Budapest, Hungary

Bradoz-1 stack composition

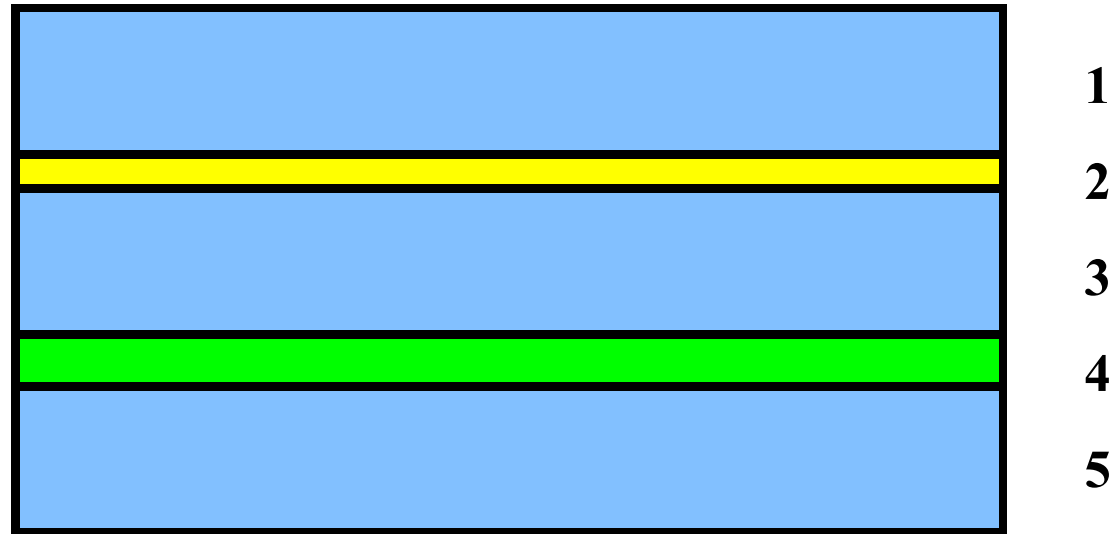


<i>Layer No.</i>	<i>Material</i>	<i>Density, g/cm³</i>	<i>Thickness, μm</i>	<i>Thickness, mg/cm²</i>
1,3,5	CR-39	1.3	1180	153.4
2	Ti	4.52	50	22.6
4	Macrofol	1.28	195	24.5

Total thickness: 507.3 mg/cm²

Area of 1 sheet: 10 cm²

7 of them were placed at different positions of the

Russian segment 'Zvezda'

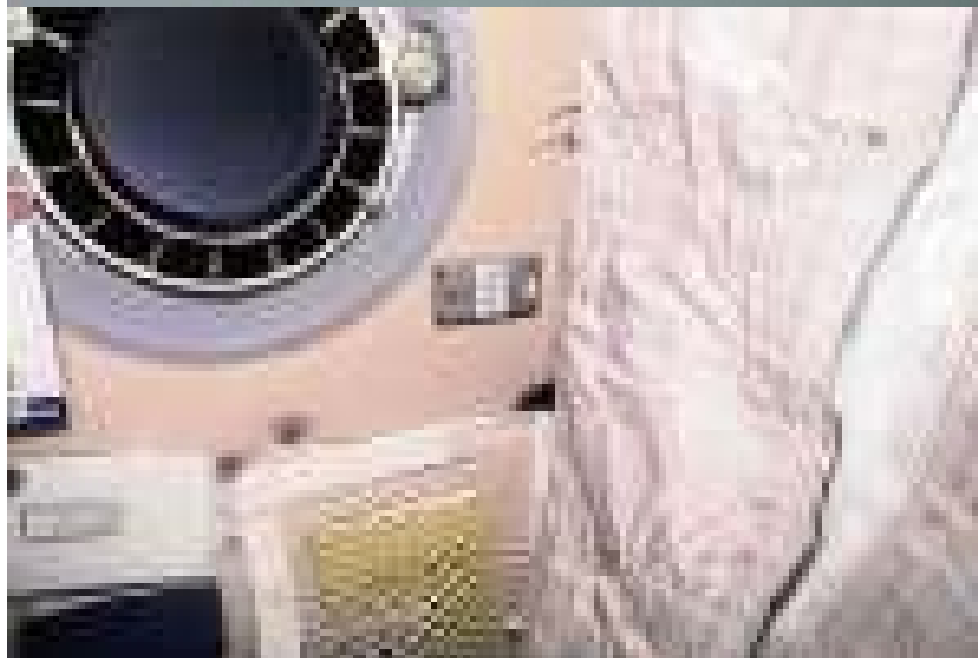

The effective shielding thickness of the panel, where the box was placed, was not provided.

Assumptions: (after Armstrong, 1998) the proton flux inside the ISS is low below 1 MeV, constant between 1 and 200 MeV (~ 3 p/cm²/s), then rapidly decreases. It is one order of magnitude below the neutron flux.

The stack position and orientation inside the box was not documented!

Assumptions: 1 mm thick Fe box filters out protons below 22 MeV. Maximum proton energy entering the box and will be detectable by the stack (on rear surface of 3rd CR-39) is ~ 50 MeV. Each surface has different upper energy limit.

Primary proton tracks can be separated from neutron induced proton tracks by multiple etching method.

What kind of particles can we expect and detect by CR-39 SSNTD inside the ISS?

Primary protons - limited detection ability, slightly disturbs neutron detection

Neutrons - by p, C and O recoils, interactions producing α and p, D and T together with scattering ions (Be), fragmentation (spallation)

Short range target fragments - mostly induced by high energy protons within the detector

Low Z particles (C, O, Ne, Mg, Si) - external origin, relatively short tracks, mostly stopping within one detector sheet, limited Z resolution because of the wall effect

Fe group and UHZE particles - external origin, may penetrate more detector sheets, high LET, bigger track diameter

Projectile fragmentation, - high LET, nearly cylindrical shape with spherical end

'Reflected light' observation


Fragments

**High Z
Fe group**

**Low Z
He, C,
O, Si**

Protons

Recoils

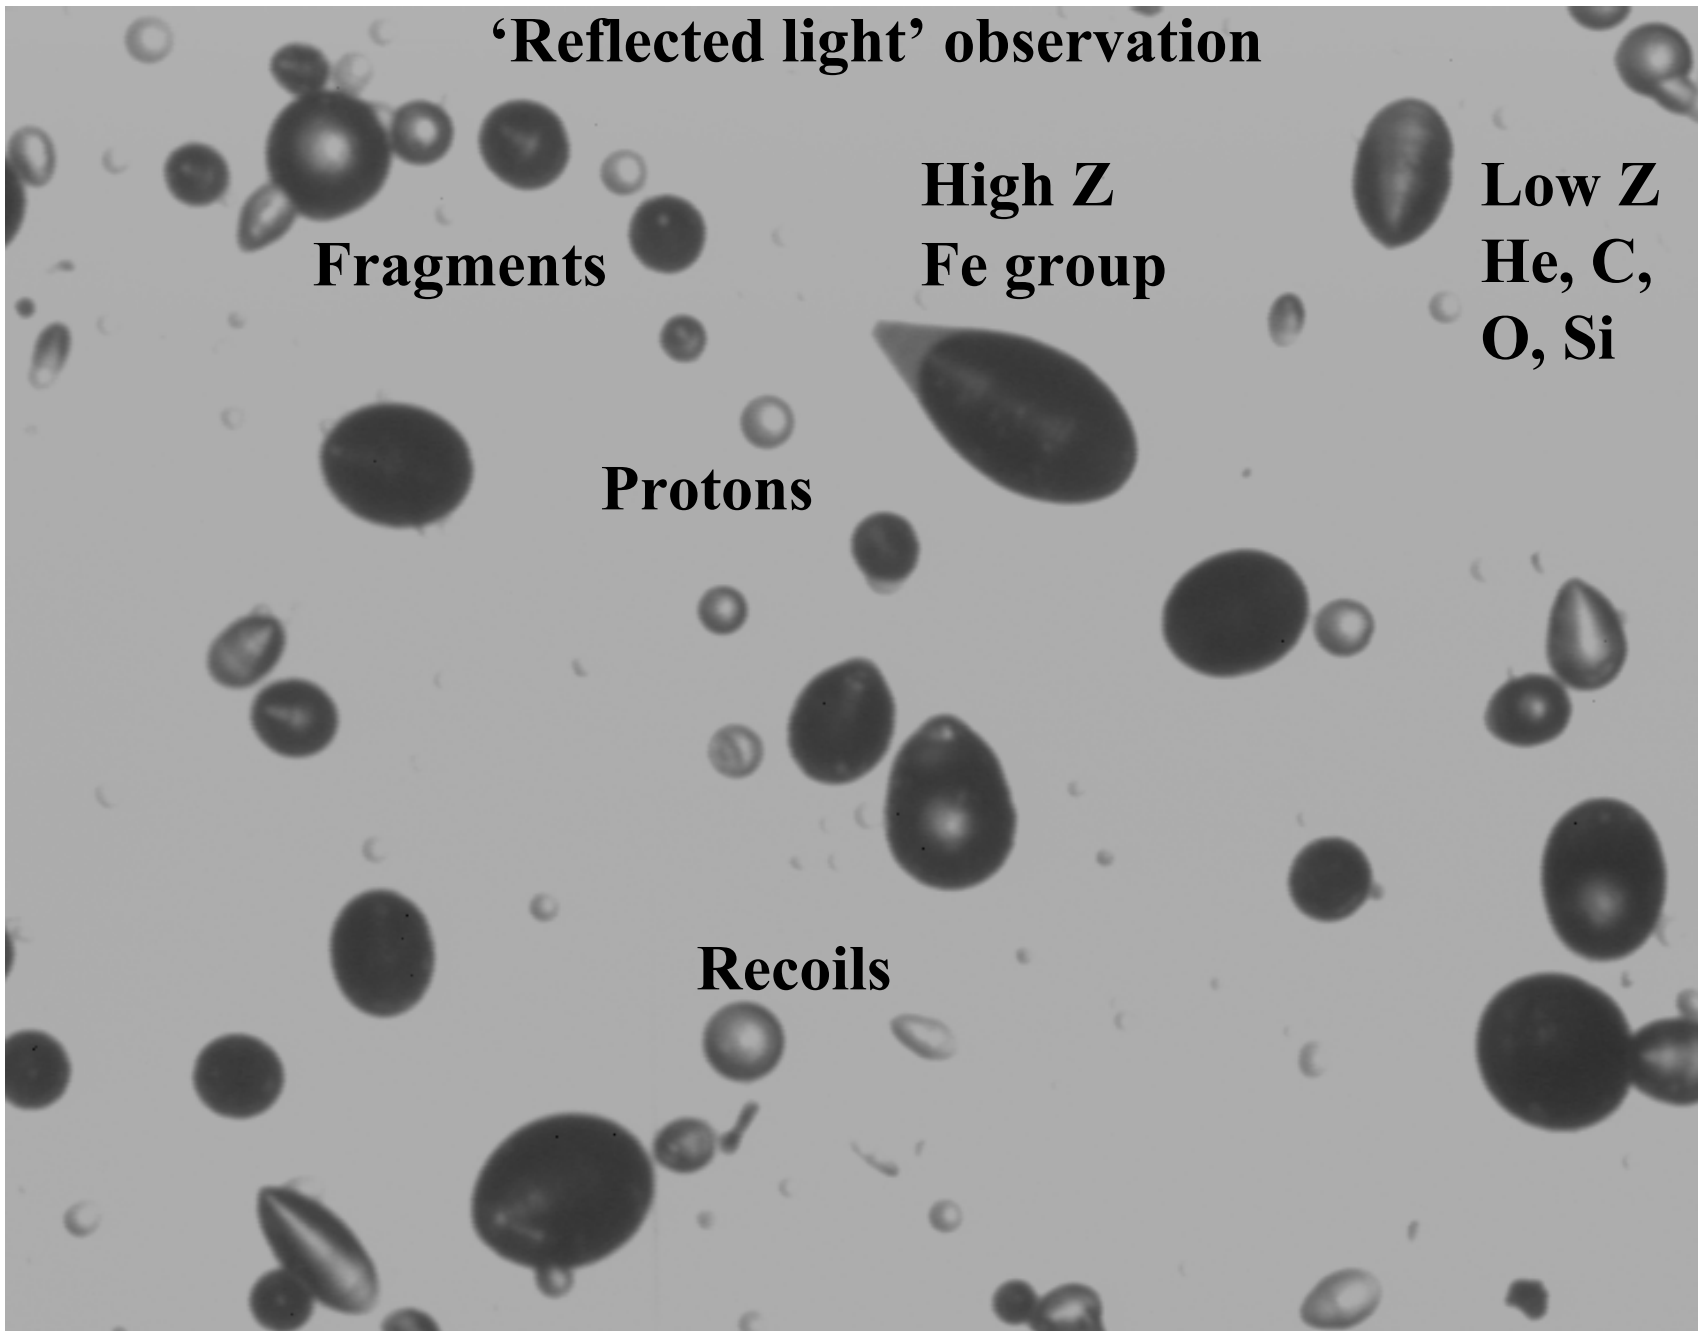

-Assessment of neutron dose-

-GCR particle tracks are distinguishable from any other ones by our pattern recognizing software and the multiple etching method. The GCR dose was not included in this discussion and would be presented later.

-The proton flux reaching the stack with energy below 20 MeV is negligible, the estimated flux above it is $\sim 6 \text{ cm}^{-2} \text{ s}^{-1}$ resulting in a high energy proton fluence of $1.3 \times 10^8 \text{ cm}^{-2}$ for the total flight time. There were few, no significant, SPE flashes. Considering the low reaction cross section (average $<50 \text{ mb}$) for the $^{12}\text{C}(\text{p},\text{pn}')^{11}\text{C}$ and $^{16}\text{O}(\text{p},\alpha)^{13}\text{N}$ reactions within the CR-39 detector we estimated <250 such events per cm^2 after 6 h etching ($\sim 8 \mu\text{m}$ layer removal). Even if all the particles produced were registered by the image analyzer they would be in minority comparing to the total track density of around 10^4 per cm^2 measured on the detector surfaces. So, we conclude that protons do not disturb the neutron detection significantly ($<3\%$ overestimation of neutron dose).

-The neutron induced charge particle production with ^{12}C and ^{16}O have thresholds, the cross sections become significant above 8 MeV for $^{12}\text{C}(\text{n},\alpha)^9\text{Be}$ ($\sim 50 \text{ mb}$) and 15 MeV for $^{12}\text{C}(\text{n},\text{n}'3\alpha)$ ($\sim 360 \text{ mb}$) reactions, respectively. In the case of $^{16}\text{O}(\text{n},\alpha)^{13}\text{C}$ reaction the threshold is at $\sim 10 \text{ MeV}$ with $\sim 1000 \text{ mb}$. The resulting particles have short range and high LET, after few hours etching their tracks become over etched (ring shaped) and well distinguishable from other tracks. Thus the neutron fraction above the thresholds can be estimated and the dose calculated. The upper detection limit is not well defined, the reaction cross sections rapidly decrease above 20 MeV, but the fraction of tracks above and below this energy cannot be estimated. If we select 20 MeV as upper detection limit, then certainly, the dose is slightly overestimated below this limit.

-Also all the other reaction (mostly producing protons) with these elements have high threshold but with lower cross section. Particles are partly detected as recoil protons causing some dose overestimation below 20 MeV.


-Direct C and O recoils tracks (from elastic collision) are detectable if the neutron energy is higher than 5 MeV. However, for both nuclei the cross section is rapidly decreasing above 20 MeV. These recoil tracks cannot be practically distinguished from the tracks of residual nuclei of (n,α) reactions.

-The neutron detection between $\sim 100 \text{ keV}$ and 8 MeV incident neutron energy is based on the neutron elastic scattering on Hydrogen atoms of the detector material. The reaction cross section is quite high, decreasing from $\sim 15.000 \text{ mb}$ at 0.1 MeV down to 1000 mb at 8 MeV. The high H content (50%) of the material and the high cross section make this reaction the most significant one. The tracks are well observable after 6 h etching and can be separated from recoils and other tracks. The detection window is between 0.12 and 8 MeV, determined by the LET and range of protons.

-The Lexan detector, which detects HZE particle only, has one more role within the stack: it works as a proton converter increasing the detection efficiency of CR-39 sheet No. 3.

-The role of the Ti foil is twofold: degrades the energy of the high energy recoiled protons coming from sheet No. 2 to fall into the detectable energy range and it works as a threshold detector utilizing the $\text{Ti}(\text{n},\text{p})\text{Sc}$ reaction. The effective threshold is at $\sim 2 \text{ MeV}$, extending the detectable neutron energy range up to $\sim 20 \text{ MeV}$.

Proton in CR-39

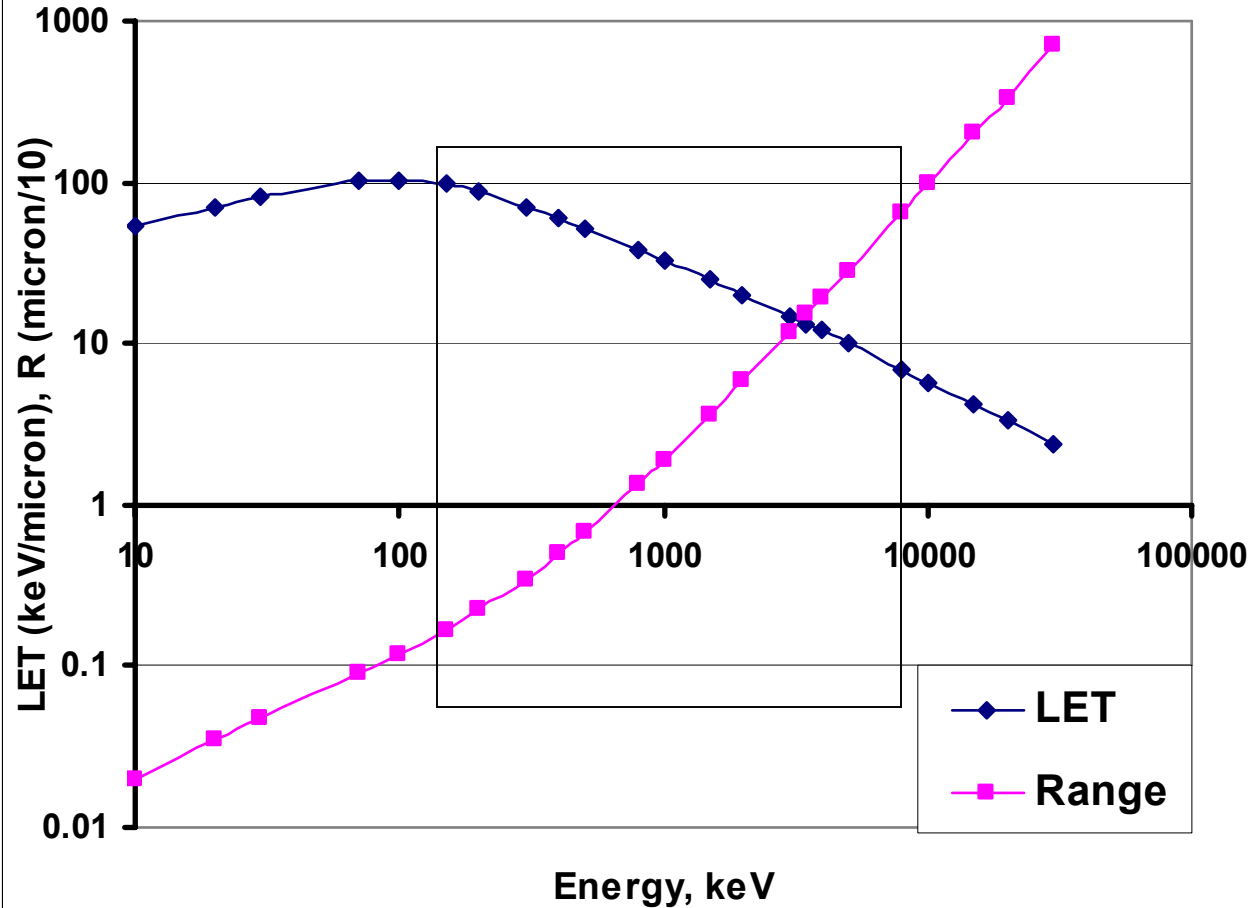

Etching: 6 h in 6N NaOH at
70 °C

Bulk etch rate: 1.34 $\mu\text{m}/\text{h}$

Detecting thresholds:


Diameter: 2 μm

Range: 1.5 μm ,

LET: 6 keV/ μm ,

Energy: 120 keV

**Maximum detectable energy
without converter:** 8 MeV

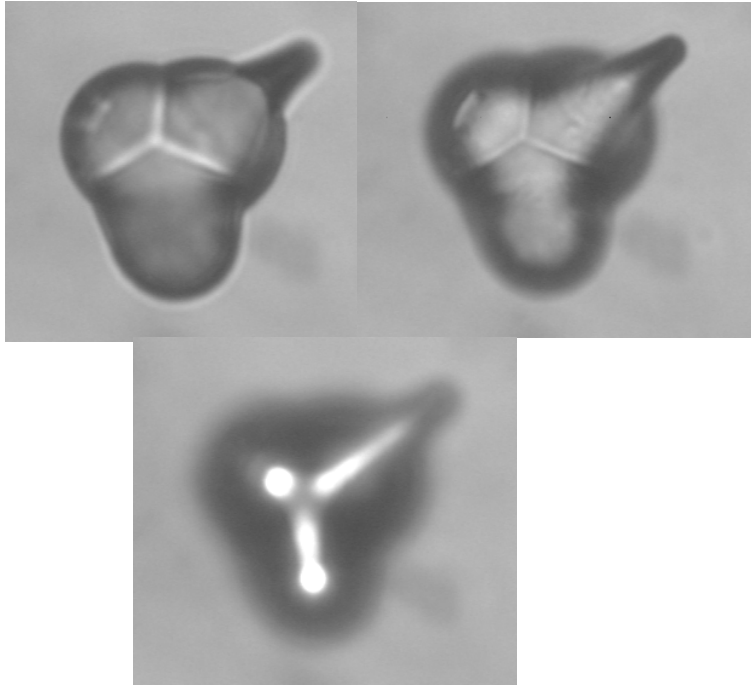

**Three-focal presentation of
tracks originated from
 $^{12}\text{C}(n,n',3\alpha)$ interaction**

**in CR-39, exposed at CERF in
CR position**

**(TASTRAK, 6n NaOH, 70 °C,
12 h etching)**

REACTION

$^{12}\text{C}(n,3\alpha)$

$^{12}\text{C}(n,T)$

$^{12}\text{C}(n,D)$

$^{12}\text{C}(n,p)$


THRESHOLD ENERGY

15 MeV

10 MeV

8 MeV


5 MeV

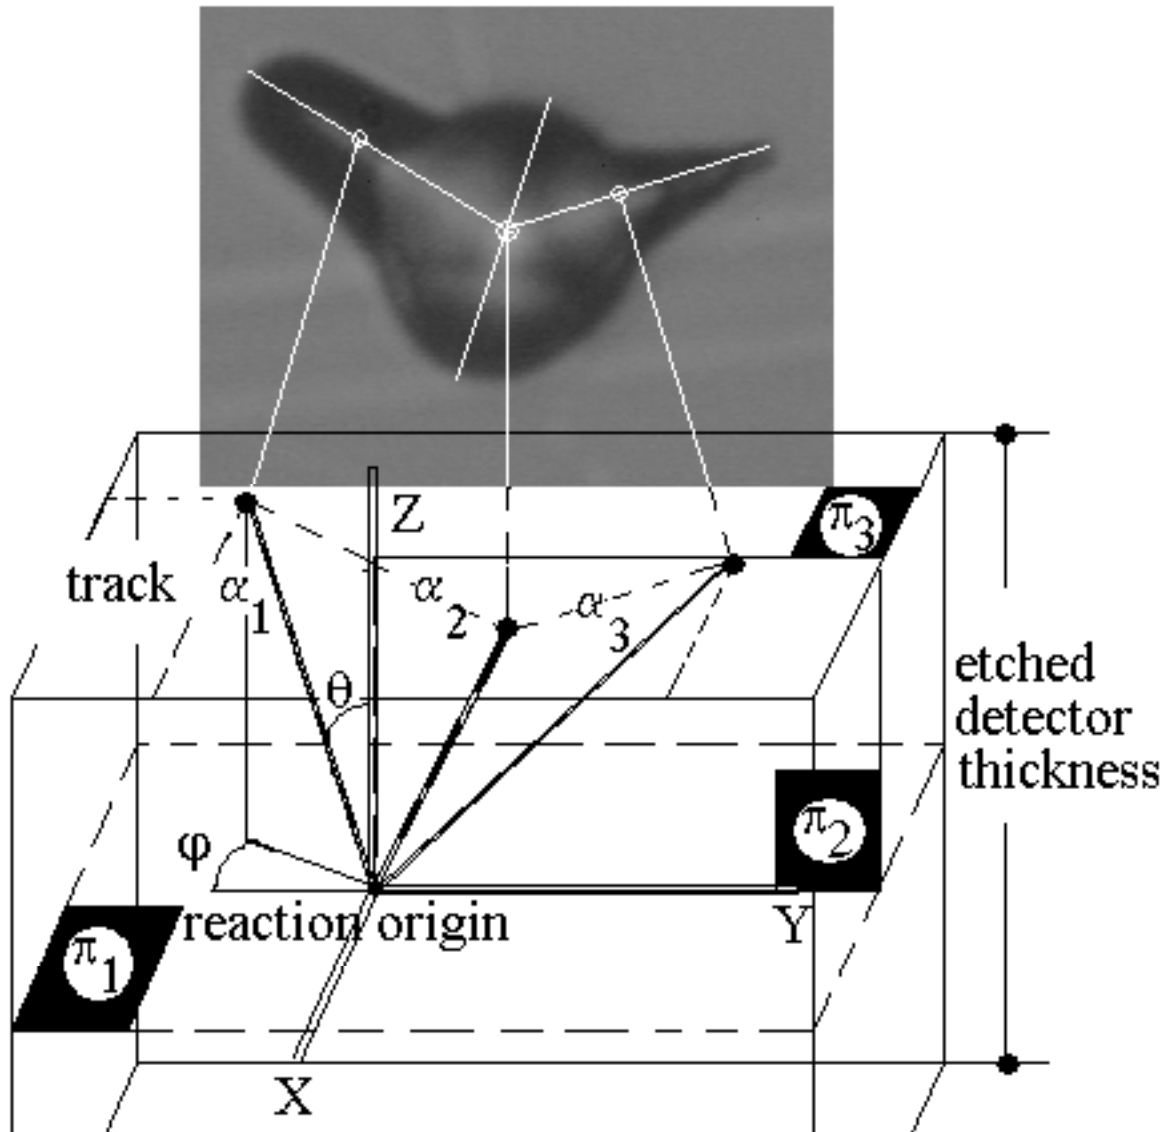

In plane π_3 we estimate the position of the latent track and from the digitalized image we deduce the geometry of the track mouth. The shape usually is the superposition of three ellipses having different eccentricity. The measured parameters allow us to determine, in principle, the direction and the range (energy) of the particles.

Reduced track diameter vs. Residual Path length

C or O recoils or target fragments, circular tracks

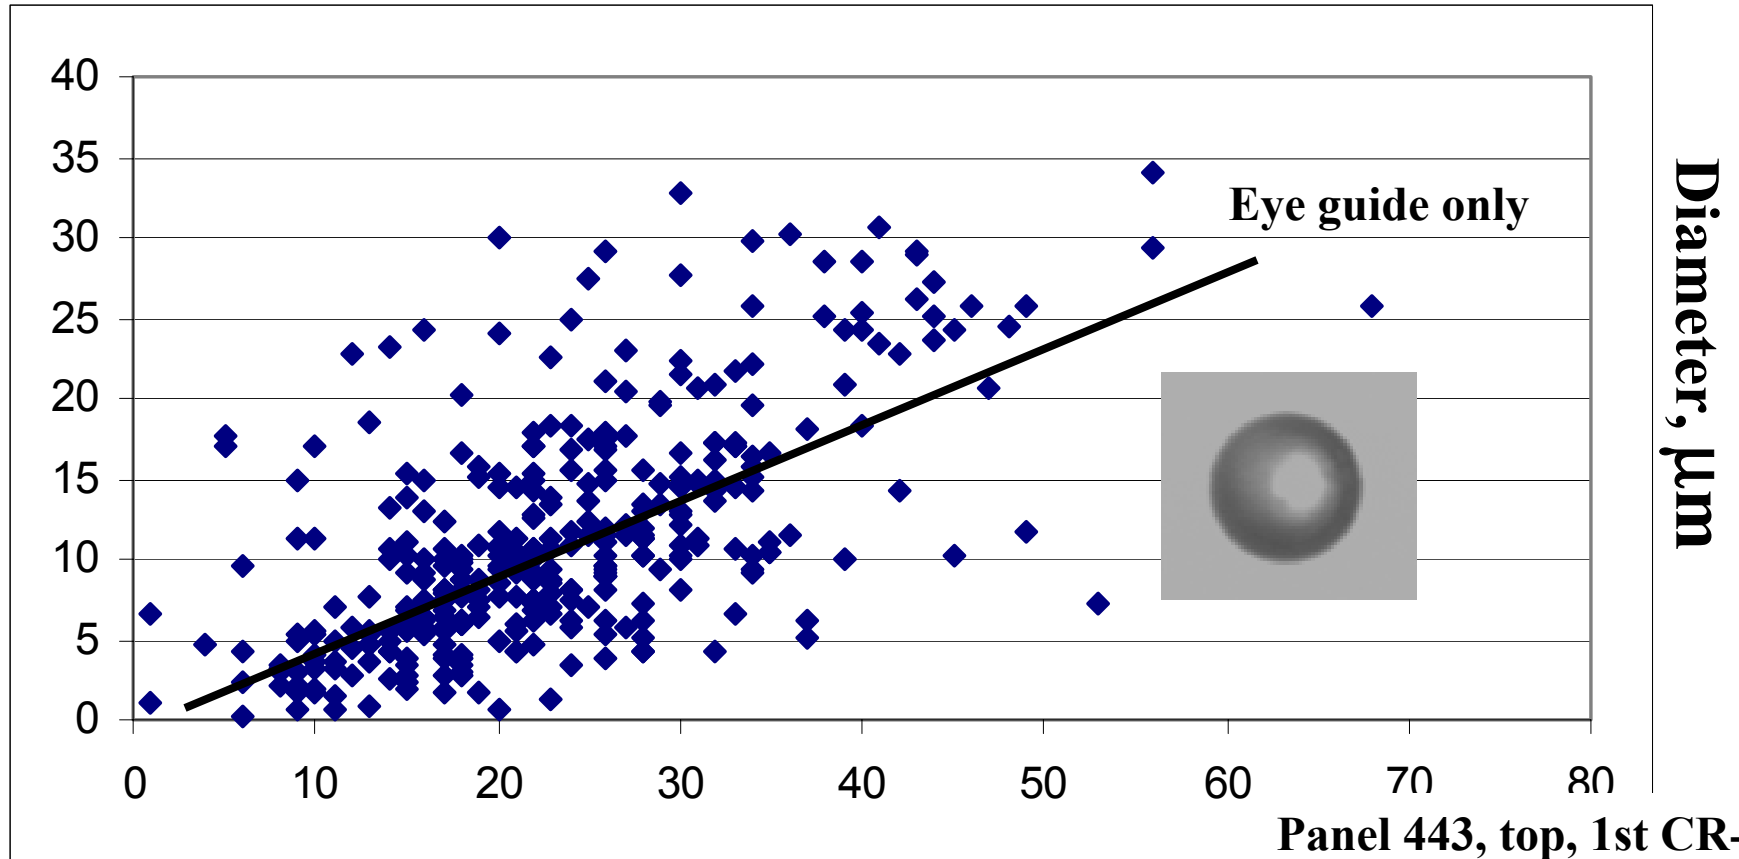

Residual Path length, μm

Removed layer: 26.8 μm

Panel 443, top, 1st CR-39 sheet

Tracks were randomly selected from the total population for illustration only

8 calibration detector stacks were exposed at CERF in the so called “concrete roof” position. Since the exposure at CERF is considered to be 2π , cosine distribution and on the ISS an isotropic field was assumed these lopsided stacks were exposed from both directions. The calibration detectors were treated together with those exposed onboard the ISS. For the dose estimate it was assumed that the neutrons reaching the detector stacks exposed both on ISS and at CERF have the same averaged fluence-to dose conversion factor.

The VIRGINIA [Palfalvi, 1997] software was taught to recognize only such type of tracks which were found on the calibration detectors. The sample tracks and their parameters were classified and stored in galleries separately for each side and each etching time (2 and 6 h). The track density measured on a given surface of the calibration detector was related to the known dose.

Stacks exposed on the ISS were investigated in the same way. Only those tracks were considered in track density and the dose calculations which were recognized by the software when compared to the learnt patterns. For each stack 6 dose values were obtained and averaged. See the results in next Table. The statistical error was always less than 10 %.

Neutron ambient dose equivalent, H*, rate at different positions of the ISS, measured in 2001

Location within the ISS


assembly, stack and panel numbers

orthogonal


	A11	A12	A13	A16	A16	A14	A15	
	Stack 1	Stack 2	Stack 3	Stack 6	Stack 7	Stack 4	Stack 5	
	443	240	110	110	110	457	318	Average
	starboard crew cabin window	port side window	...floor, beside window 6...			starboard lavatory	ceiling	
light shield.....				heavier shield....		
H*	52	39	47	68	63	54	73	56.6
μSv/d								± 21%

Energy range: 200 keV - 20 MeV, Overall uncertainty: < 30%

**Calculated neutron spectrum
inside the ISS [Armstrong, 1998]**

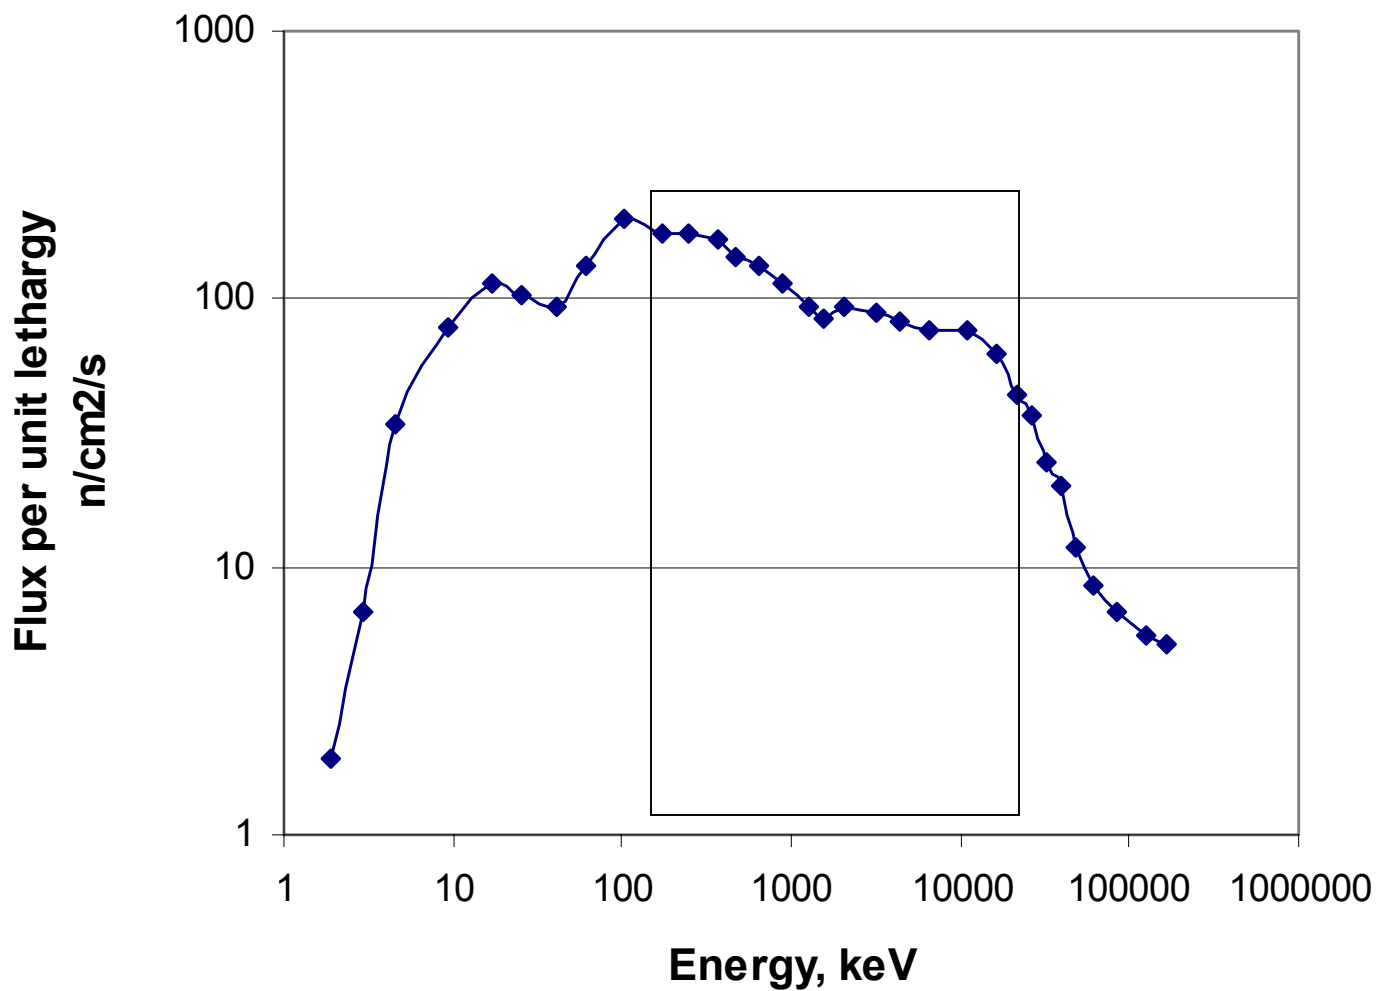

- Since the CERF calibration spectrum (concrete roof) is somewhat different from the spectra at different positions inside the ISS, the overall uncertainty of the averaged dose rate at a given position has been estimated by sensitivity analysis and found to be below $\pm 30\%$ for each location.
- The dose in 0.2 – 20 MeV range can be 60 % of the total neutron dose as calculable from the predicted neutron spectrum shown here. This would result in an averaged total neutron ambient dose equivalent of about 94 $\mu\text{Sv/d}$.
- Since the standard deviation of the averaged dose value is 21% and the overall uncertainty of each measurement is $\pm 30\%$, it can be said, that the doses are not significantly different on the different places. Similar conclusion was obtained from the DOSMAP Experiment carried out in other segments of the ISS in 2001.

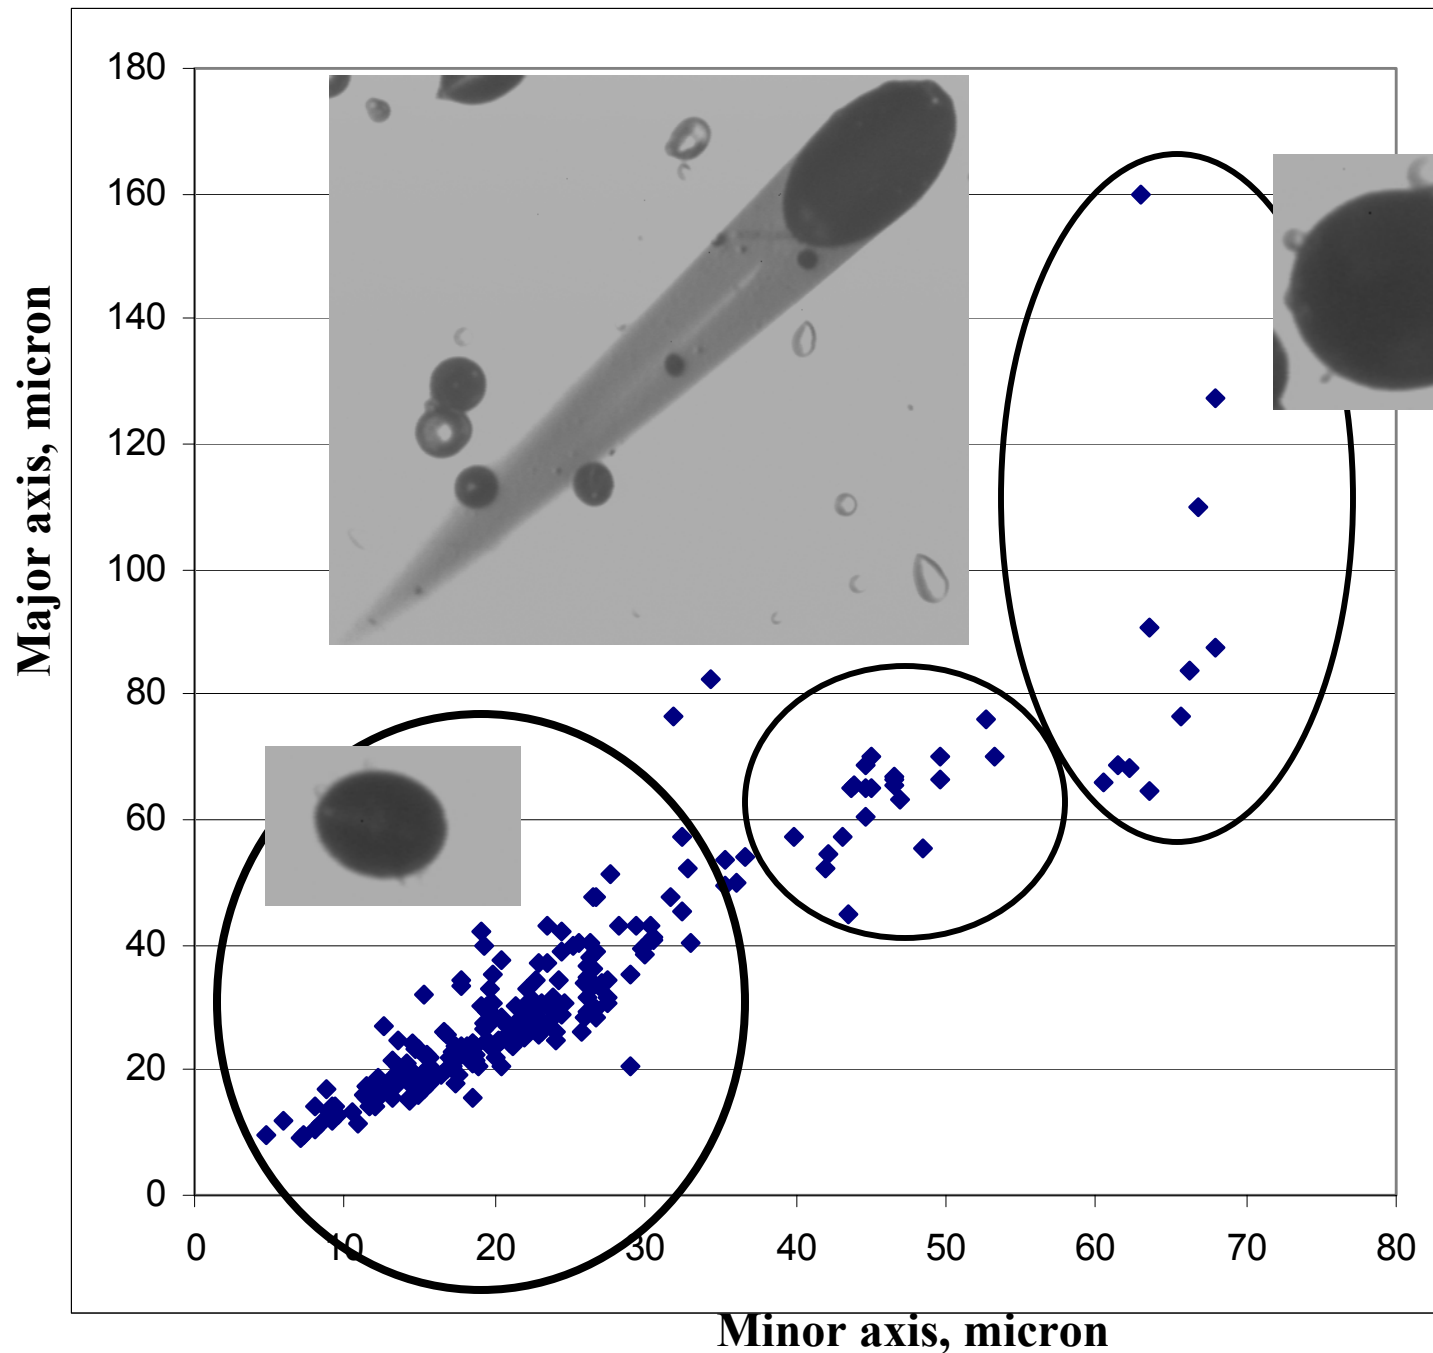


**GCR
particle
tracks of
different
origin**


**Panel 443, top,
1st CR-39 sheet**

**Tracks were
randomly
selected from the
total population
for illustration
only**

Special attention was devoted to study cylindrical like tracks

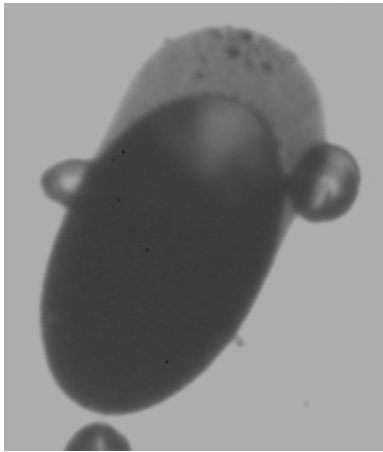

**Focusing
onto
upper
surface**

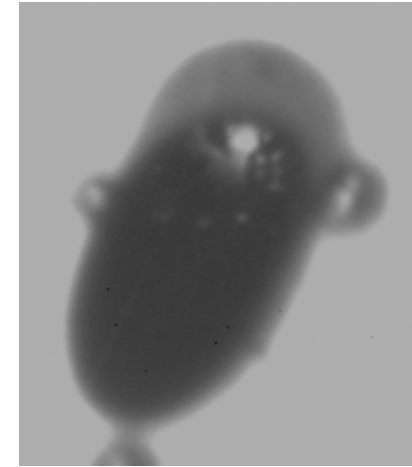


**Focusing
onto
track end**


The origin of such tracks has not been clarified yet.

Properties:

- No matching tracks were localized on other surfaces
- Tracks are nearly cylindrical and have spherical end
- The length of the minor axes are very similar and the biggest among other measured ones

More details on next 3 pages

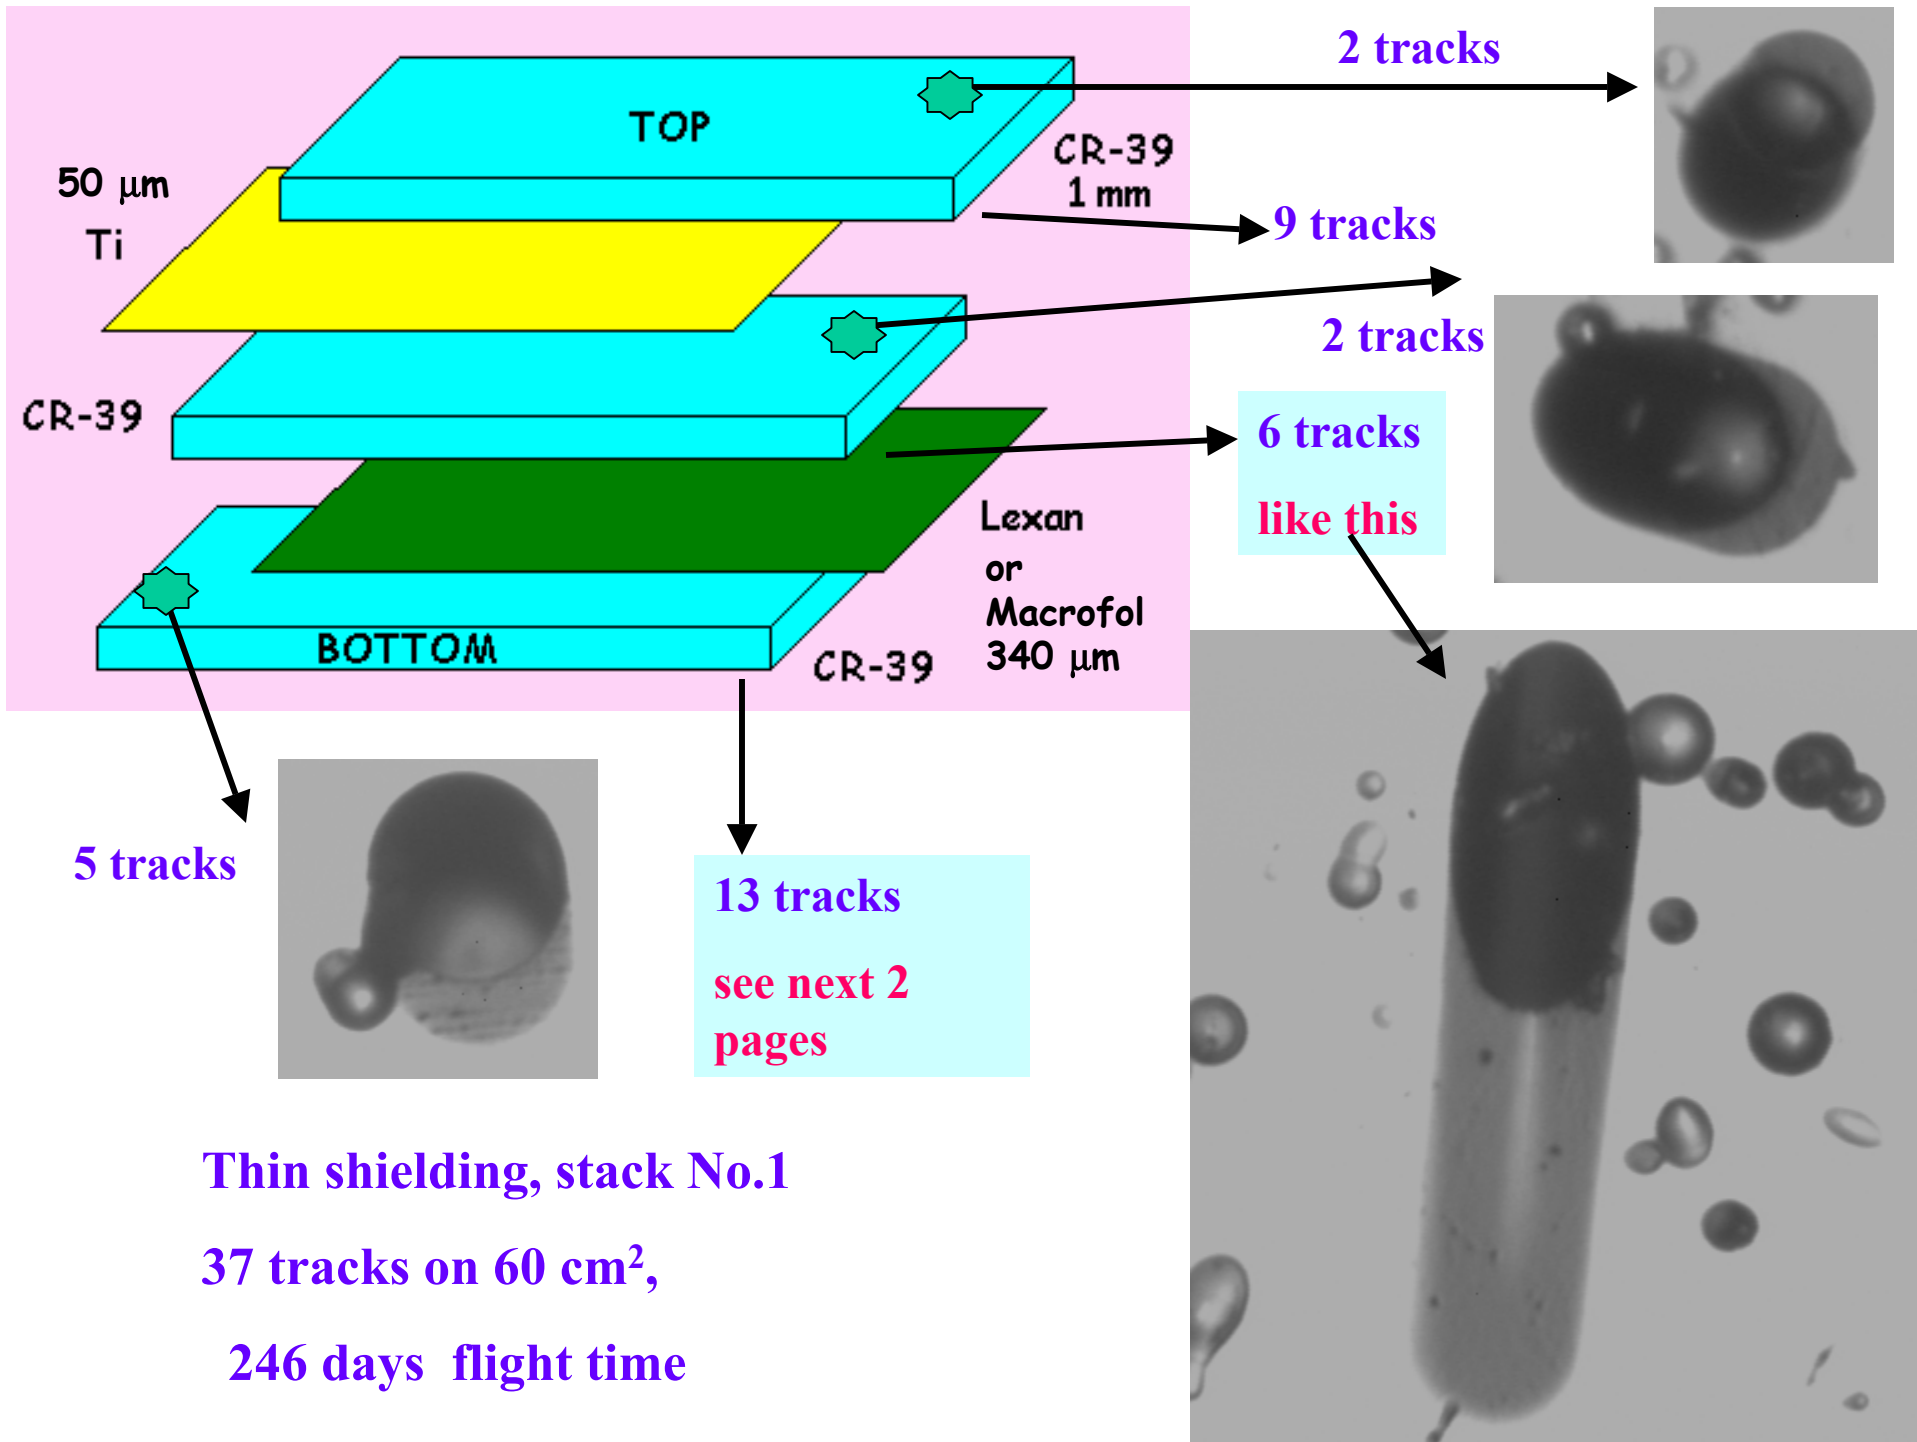

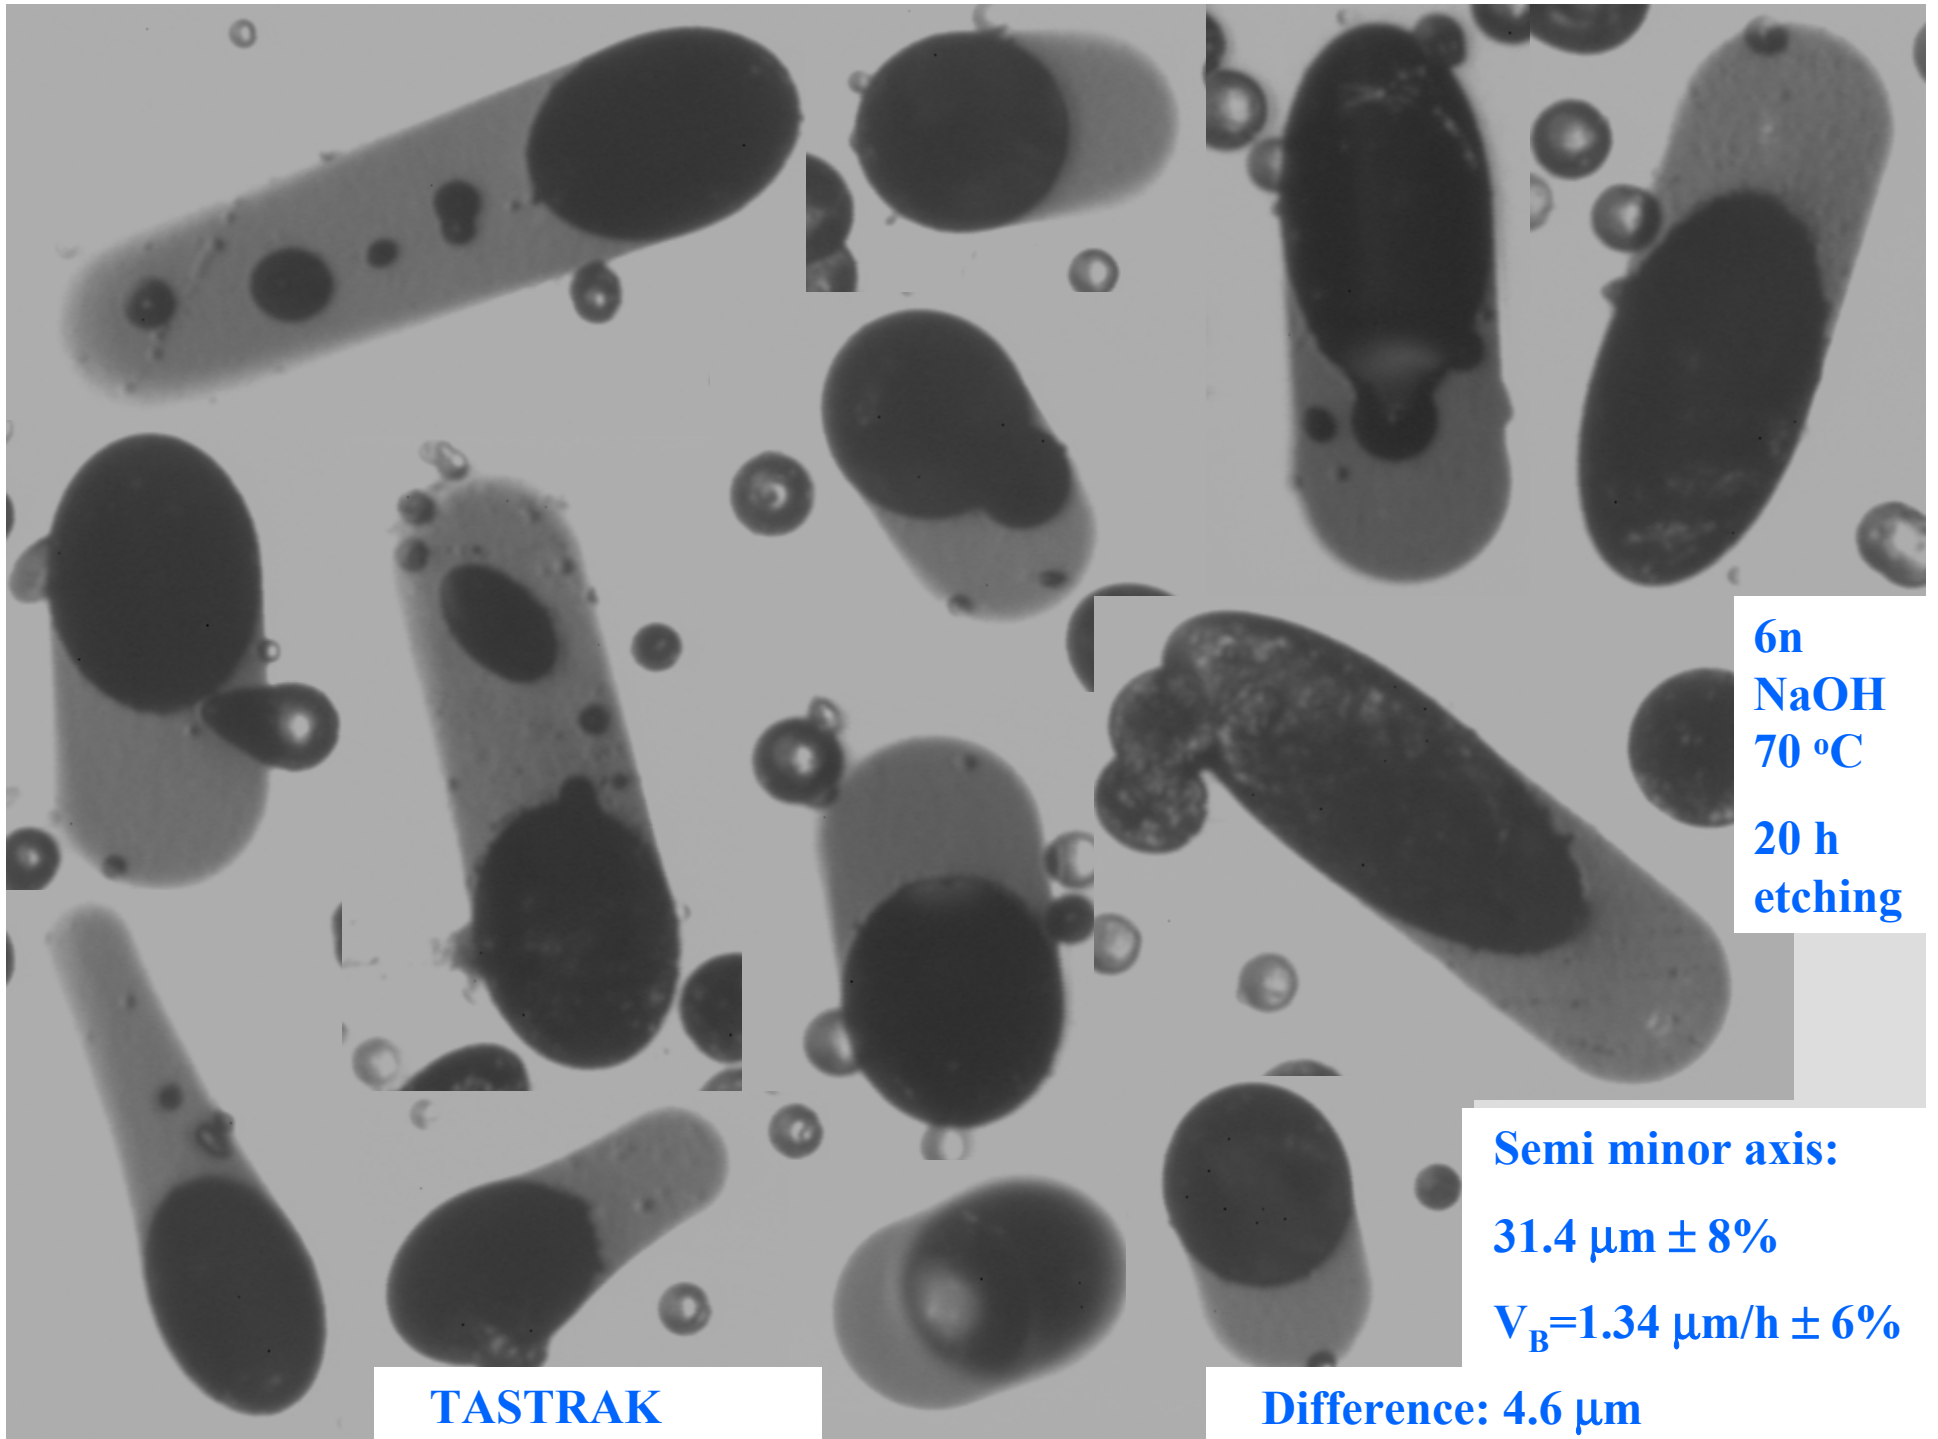

6n
NaOH
70 °C
20 h
etching


TASTRAK

Semi minor axis:
31.4 $\mu\text{m} \pm 8\%$
 $V_B=1.34 \mu\text{m/h} \pm 6\%$

Difference: 4.6 μm

Track Number	Reconstructed path length in detector μm	Minor axis on etched surface μm	Incident angle degree	Diameter of spherical track end μm
1	261.1	63.6	47.3	54.8
2	158.4	66.8	50.6	63.8
3	121.8	65.6	35.6	66.0
5	178.7	63.0	65.3	63.0
6	159.5	67.9	58.0	66.0
8	74.4	62.3	36.1	60.2
9	99.3	60.5	26.7	53.7
10	162.8	61.4	17.7	57.5
11	138.0	68.0	43.2	62.7
13	211.8	66.3	40.3	57.4
14	137.2	63.5	26.3	56.0
Average (11)	-	64.4 ± 2.6 (4.1%)	-	60.1 ± 4.45 (7.4%)
7	157.7	53.3	32.9	36.4
12	204.6	52.7	48.4	26.1
Average (13)	-	62.7 ± 4.9 (7.8%)	-	-


Etched off layer,
26.8 μm

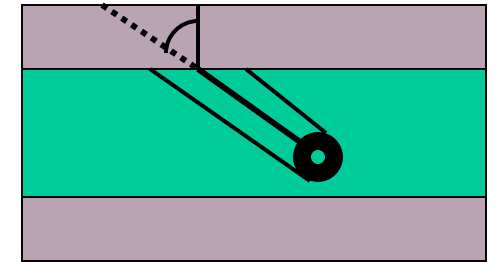

$$V_B = 1.34 \mu\text{m/h}$$

$$t = 20 \text{ h}$$

Uncertainty of length measurements $< 1,1 \mu\text{m}$ at 96% confidence level, based on α track diameter measurements, at overall magnification = 400

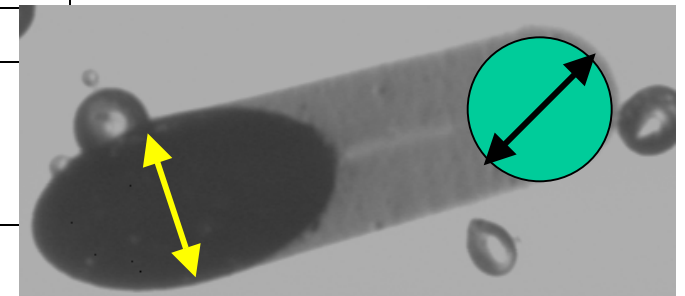

References

T. W. Armstrong, B. L. Colborn, 2001, Rad. Meas. **33**, 229-234

D. Nikezic, K. N. Yu, 2000 & 2003, Rad Meas. **32**, 277-282 & **37**, 39-45 & **37**, 595-601

J. K. Palfalvi, I. Eördögh, K. Szász, and L. Sajó-Bohus, 1997, New Generation Image Analyzer for Evaluating SSNTDs, Radiat. Meas. **28**, 849-852.

Acknowledgement

This work was partly supported by the Hungarian Space Office (MÜI), project No. TP-174.

MISSION INFORMATION

Stacks launched on 26-02-2001 by Progress 244

Returned to Earth on 31-10-2001 by Sayuz TM-32

Received by AEKI on 28. 03. 2002.

Some results presented on WRMISS in Paris, Sept. 2002

Evaluation is still in progress (2003-2004)